

Montmorillonite Nanoparticles Effectiveness in Removal of Amoxicillin from Water Solutions

Davoud Balarak¹, Fatemeh Ganji², Kethineni Chandrika³, Shaziya Haseeb^{4*}

¹Department of Environmental Health, Health Promotion Research Center, Zahedan University of Medical Sciences, Zahedan, IRAN.

²Department of Environmental Health- Student Research Committee, Zahedan University of Medical Sciences, Zahedan, IRAN.

³Department of Biotechnology, Koneru Lakshmaiah Education Foundation, Vaddeswaram, Guntur, Andhra Pradesh, INDIA.

⁴Environmental Research Laboratory, Department of Applied Chemistry, Aligarh Muslim University, Aligarh, Uttar Pradesh, INDIA.

ABSTRACT

Objectives: In this article, novel montmorillonite nanoparticles (MON-NP) evaluated in order to facilitate the sorption of Amoxicillin (AMO) from aqueous solutions in batch operations. **Methods:** Batch experiments were performed to study the influence of various experimental parameters such as contact time, adsorbent dosage, initial concentration of the AMO and temperatures at fixed solution pH. The Langmuir, Freundlich and Dubinin-Radkovich (D-R) models were subjected to sorption data to estimate sorption capacity, intensity and energy. **Results:** The optimum conditions of sorption were found as follows: a sorbent amount of 0.8 g in L of AMO solution (10 mg/L), contact time 90 min at fixed pH and temperature 7 and 25°C, respectively. To study the kinetics of removal process, three equations, i.e. Morris-Weber, Lagergren (pseudo first order) and pseudo second order were used. The AMO sorption process was well described by the

pseudo second order kinetic model. The maximum adsorption capacity (q_e) from Langmuir isotherm model was determined to be 39.41 mg/g and for D-R isotherm was 32.47. **Conclusion:** The results indicate that MON-NP could be employed as a low-cost in wastewater treatment for the removal of AMO.

Key words: Montmorillonite, Nanoparticles, Amoxicillin, Isotherm, Kinetic.

Correspondence

Dr. Shaziya Haseeb

Environmental Research Laboratory, Department of Applied Chemistry, Aligarh Muslim University, Aligarh-202002, Uttar Pradesh, INDIA.

Email: mbehdash75@gmail.com

DOI: 10.5530/ijpi.2020.2.22

INTRODUCTION

With the widespread use of antibiotics, pharmaceutical effluents containing antibiotics have recently attracted wide attentions since it has potential adverse effects.^{1,2} Although the injuriousness of antibiotics is not so intuitive like other environmental pollution, residues of the antibiotic drug have become a seriously ignored problem.^{3,4} The abuse of antibiotics can damage the immune function of animals, when again infected and then they need more antibiotics to treat. Thus, it could sink into a vicious cycle.^{5,6}

In recent years, the adsorption process has been considered for removal of many elements.⁷ The operation of adsorption process is dependent on many parameters such as pH, the kind of adsorbent and the kind of pollutant.^{8,9} For this purpose, many adsorbents for removal of antibiotics have been used such as activated carbon, brick powder, activated alumina and charcoal.^{10,11} Activated carbon has been widely used for this purpose because of its high adsorption capacity. However, its high cost sometimes tends to limit its use.^{12,13}

Clays are widely applied in many fields such as polymer nano-composites, adsorbent, catalysts, photochemical reaction fields, ceramics, paper filling and coating, sensors and biosensors, due to their high specific surface area, chemical and mechanical stabilities and a variety of surface and structural properties.^{14,15} The most-used clays as nano-adsorbents are montmorillonite/smectite group and kaolinite group clays.^{16,17}

This paper reports on the ability of montmorillonite clay (MC) to remove AMO from aqueous solution.¹⁸ Clay has already been shown to have a high adsorption capacity, which may even exceed that of activated carbon under the same conditions of temperature and pH.¹⁹

For the present study, a batch-contact-time method was used and the equilibrium of AMO adsorption on to MON-NP was investigated with attempts to fit the data to Langmuir, Freundlich and Dubinin-Radushkevich (D-R) equations. The uptake of AMO on MON-NP was examined as a function of adsorbate concentration, adsorbent concentration and contact time.

MATERIALS AND METHODS

Amoxicillin (CAS Number 26787-78-0; chemical formula, $C_{16}H_{19}N_3O_4S$; MW, 365.40 g/mol) was used as the adsorbent in this study obtained from Sigma Aldrich Co; it was used without further purification. A Montmorillonite nanoparticle was obtained from the Iranian Nanosony Corporation and was used without further purification.

The 1000 mg/L stock solution of AMO was prepared by dissolving 1 g of AMO powder in one liter of distilled water. In the present study, Laboratory Erlenmeyerflasks were used for adsorption experiments. Batch sorption experiments were performed at a constant temperature of 25°C on a magnetic mixer at 150 rpm. Through the dilution of 1 g/L stock solutions, 100 mL of the AMO solution was prepared for each adsorption test. Using the diluted solution of hydrochloric acid or sodium hydroxide, the initial pH was adjusted to variable values. Also different concentrations of AMO (10, 25, 50, 100 mg/L) at various dosage of nano adsorbent (0.1, 0.2, 0.4, 0.6, 0.8 and 1 g/L) at different reaction times were studied for the optimization of the AMO removal process with MON-NP. After that, the solutions were filtered through a 0.45 µm filter and finally AMO concentrations were measured with a spectrophotometer (HACH DR 5000) at 280 nm wavelength. The

This is an open access article distributed under the terms of the Creative Commons Attribution-NonCommercial-ShareAlike 4.0 License, which allows others to remix, tweak, and build upon the work non-commercially, as long as the author is credited and the new creations are licensed under the identical terms.

adsorption capacity of MON-NP in the removal of AMO was calculated using the following equation:^{20,21}

$$q_e = \frac{(C_0 - C_e) \times V}{M}$$

Where C_0 is initial concentration of AMO (mg/L), C_e is final concentration of AMO (mg/L), M is mass of adsorbent (g) and V is volume of solution (L).

RESULTS

The SEM images give information about the surface morphology. Figure 1. Show the SEM images of MON-NP. According to SEM images, MON-NP are stacks of multi-layers with a sheet structure. Regarding to this Figure, these nanoparticles consist of irregular morphology with a size of a few micrometers. Furthermore, the heterogeneous surface of the particles is clear.

Figure 2 shows the amounts of AMO adsorption on MON-NP adsorbent with dosages of 0.1, 0.2, 0.4, 0.6, 0.8 and 1 g/L. Figure 3 shows that with increasing the adsorbent masses, the adsorption capacities of the adsorbents decreases. So the maximum amount of adsorption with MON-NP occurred when the adsorbent mass was 0.2 g/L.

The adsorption of AMO on MON-NP was investigated as a function of contact time (10–150 min) at concentrations of 50 mg/L with an initial solution pH of 7. It was noticed that AMO removal increased with time (Figure 3). AMO uptake by MON-NP increased when the initial AMO concentration increased from 10 to 100 mg/L (Figure 4).

ADSORPTION KINETIC

The kinetic data of AMO adsorption onto MON-NP was used in Morris-Weber (following Equation) to examine the change in the concentration of sorbate onto sorbent with contact time.

$$q_t = K_{id} t^{1/2} + C$$

Where q_t is the sorbed concentration of AMO at time 't'. The Morris-Weber transport (K_{id}) rate constant value is calculated from the slope of the linear plot of Figure 5 (q_t versus $t^{1/2}$).

In Lagergren, a pseudo-first-order equation was suggested for the sorption of liquid/solid system based on solid capacity. It is assumed in this equation that the rate of change of sorbate uptake with time is proportionate to the difference in the saturation concentration and the

amount of solid uptake with time. The Lagergren equation is mostly used in liquid phase sorption. The general equation is given as:²³

$$\text{Log}(q_e - q_t) = \text{Log } q_e - \frac{K_1 t}{2.3}$$

Where q_e is the sorbed concentration at equilibrium and K_1 is the first order rate constant. The linear plot of $\text{log}(q_e - q_t)$ against time 't' reveals the applicability of the above equation for AMO sorption onto MON-NP. The sorption of AMO onto MON-NP following pseudo-second-order kinetics is expressed as Equation:²³

$$\frac{t}{q_t} = \frac{1}{K_2 q_e^2} + \frac{t}{q_e}$$

Where q_t denotes the amount of AMO adsorbed at time t and q_e shows that amount at equilibrium (mg/g). Also, K_2 (g/mg.min) is the pseudo-second-order rate constant for the adsorption process. The rate equations and the related values are given in Table 1. The best-fit model was selected based on the match between experimental ($q_{e, \text{exp}}$) and theoretical ($q_{e, \text{cal}}$) uptake values and linear correlation coefficient (R^2) values at four studied concentrations. The values obtained by pseudo-second-order model (Figure 6 and Table 1) were found to be in good agreement with experimental data and can be used to favorably explain the AMO adsorption on MON-NP.

Adsorption isotherms

To study the adsorption isotherms the experimental data were analyzed using Freundlich, Langmuir and Dubinin-Radushkevich (D-R) isotherm models. The linear forms of Langmuir, Freundlich and D-R can be expressed as follows:²⁴

$$\frac{C_e}{q_e} = \frac{1}{q_m K} + \frac{C_e}{q_m} \quad R_L = \frac{1}{1 + K C_0}$$

$$\text{Log } q_e = \text{Log } K_F + \frac{1}{n} \text{Log } C_e$$

$$\text{Ln } q_e = \text{Ln } q_m - \beta \epsilon^2 \quad E = \frac{1}{\sqrt{2\beta}}$$

Where q_e is the equilibrium concentration of AMO in the solid phase (mg/g), q_m is the maximum adsorption (mg/g), K is the Langmuir adsorption equilibrium constant (L/mg), K_F is the Freundlich constant representing the adsorption capacity (mg/g)(l/mg)ⁿ and n is the Freundlich constant representing the intensity of adsorption. Also at D-R Eq where q_e is the amount of AMO adsorbed per unit dosage of the adsorbent (mg/g); q_m denotes the monolayer capacity; β indicates the

Table 1: The results of kinetic model studies related to the AMO adsorption onto MON-NP.

AMO Concentration (mg/L)	$(q_e)_{\text{exp}}$	Intraparticle diffusion model			Pseudo-first order			Pseudo-second order		
		K_{id}	I	R^2	$(q_e)_{\text{cal}}$	K_1	R^2	$(q_e)_{\text{cal}}$	K_2	R^2
10	9.971	0.613	3.571	0.774	4.147	0.034	0.812	9.241	0.0072	0.999
25	23.49	1.623	6.114	0.814	11.92	0.051	0.859	24.18	0.0059	0.998
50	45.93	3.256	8.358	0.823	23.59	0.063	0.834	39.74	0.0047	0.998
100	82.72	6.045	11.82	0.805	41.68	0.067	0.861	84.36	0.0041	0.996

Table 2: Isotherms constants for the removal AMO onto MON-NP.

Langmuir				Freundlich			D-R		
q_m	R_L	K_L	R^2	n	K_F	R^2	E	q_m	R^2
39.41	0.041	0.144	0.998	3.47	9.451	0.847	6.476	32.47	0.925

activity coefficient related to the mean sorption energy and finally ϵ is the Polanyi potential.

DISCUSSION

As can be concluded from the results, due to greater availability of the exchangeable sites or surface area at higher concentrations of the adsorbent, with increasing of adsorbent dosage from 0.2 g/L to 1 g/L, the removal efficiency of AMO increased. This was due to increasing collisions and also free bond on adsorbent surfaces.^{23,25}

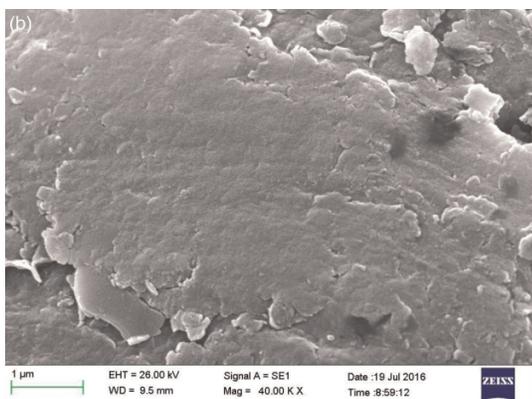


Figure 1: SEM images of montmorillonite nanoparticles.

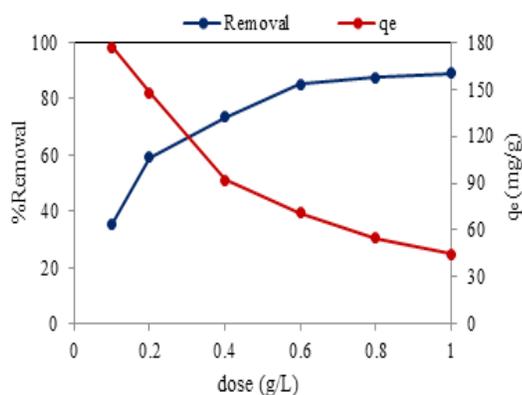


Figure 2: Effect of adsorbent dose on AMO removal efficiency ($C_0 = 50$ mg/L, pH=7, Contact time=90 min).

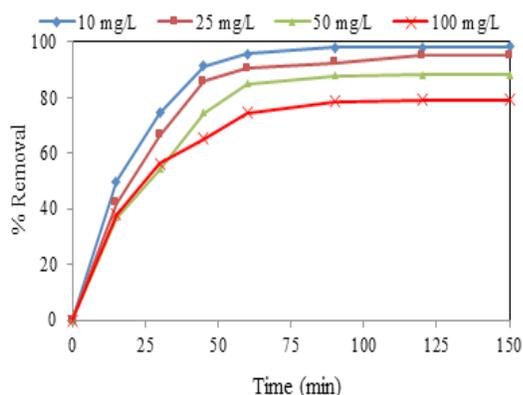


Figure 3: Effect of contact time on AMO removal efficiency (pH=7 and adsorbent dose=0.8 g/L).

The trends of the plots in Figure 3 exhibit that AMO uptake was rapid in the beginning followed by a slower removal that gradually reached a plateau.²⁴ Maximum removal of AMO was achieved within the first 45 min of contact time and equilibrium was attained in 90 min. There was no significant change in AMO uptake by MON-NP in the following 150 min. Similar results were observed by Yu who investigated the effect of contact time on removal of tetracycline from aqueous solution by carbon materials and indicated that adsorption increases with increasing contact time.³

The effect of initial AMO concentration on equilibrium adsorption was also investigated at five different initial AMO concentrations

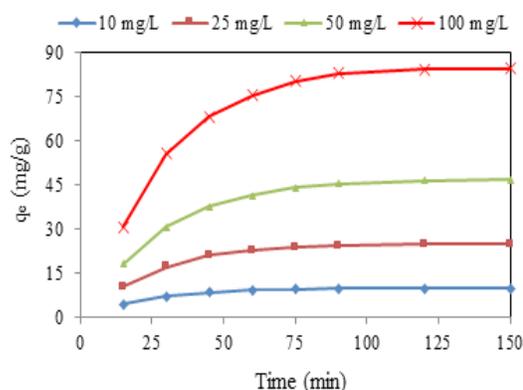


Figure 4: The effect of initial concentration on the adsorption capacity (pH=7 and adsorbent dose =2.5 g/L).

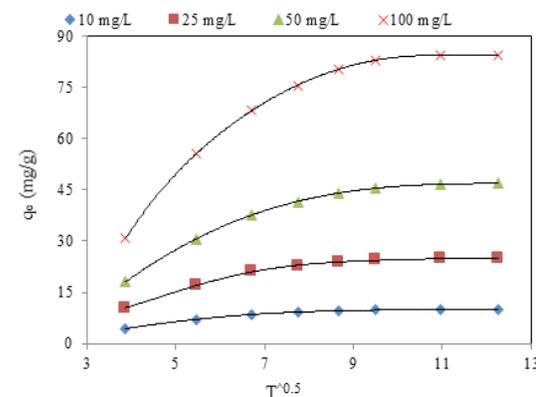


Figure 5: Intra-particle diffusion plots for of AMO adsorption onto MON-NP.

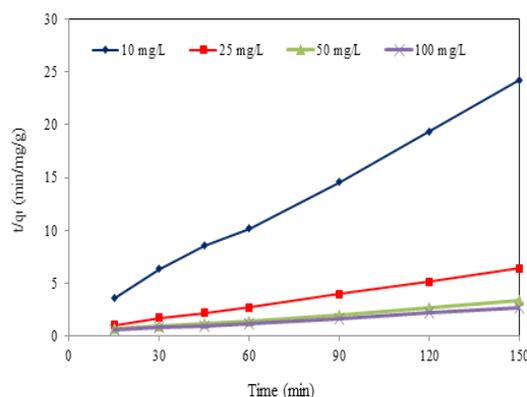


Figure 6: Pseudo-second order kinetics of AMO adsorption onto MON-NP.

(10-100 mg/L). AMO uptake by MON-NP increased when the initial AMO concentration increased from 10 to 100 mg/L (Figure 5). This behaviour can be explained due to the increase in the driving force of the concentration gradient, as an increase in the initial AMO concentration.²⁶ Such phenomenon is common in a batch reactor with either constant adsorbent dose or varying initial adsorbate concentration or vice versa.^{22,27}

Most of adsorption processes in various solid phases depend on the time element. Knowledge of the kinetics of these processes is important to understand the dynamic interactions of AMO with MON-NP and predict the rate of adsorption with time. Some kinetic models, i.e. Morris-Weber, Lagergren and pseudo second order models were used for their validity with the experimental adsorption data for the adsorption of AMO onto MON-NP. These models were supposed to offer no mass transfer (both external and internal) resistance to the overall adsorption process.²⁸ A study was conducted on the adsorption kinetics and the findings suggest that these rates along with the solute uptake rate control the residence time of adsorbate uptake at the solid-solution interface including the diffusion process.^{29,30}

The intra-particle diffusion approach can be used to predict if intra-particle diffusion is the rate-limiting step. The data exhibit multi-linear plots, revealing that the process is governed by two or more steps (Figure 6). The first linear portion (phase 1) at both concentrations, can be attributed to the immediate utilization of the most readily available sorbing sites on the sorbent surface. Phase 2 may be attributed to very slow diffusion of the sorbate from the surface site into the inner pores. Thus initial portion of AMO sorption by MON-NP may be governed by the initial intra-particle transport of AMO controlled by surface diffusion process and the later part controlled by pore diffusion.³¹

Table 2 presents the statistical results together with the isotherm constants. Results suggest that the AMO adsorption by MON-NP can be matched using the Langmuir equation. Also, the D-R equation suggests there is a considerable correlation factor. It can be understood from the D-R isotherm that the heterogeneity of energies is close to the adsorbent surface. The quantity is related to the mean sorption energy, E , which is the free energy for the transfer of 1 mole of AMO from the infinity to the surface of the adsorbent.²⁷ It is clear that we can use the E magnitude to estimate the adsorption type. If this value goes below 8 kJ/mol, the adsorption type is expressed by the physical adsorption and between 8 and 16 kJ/mol the adsorption type can be explained by ion exchange.²⁸ In this study, the E values were below 8 kJ/mol. This reveals that the adsorption of AMO onto MON-NP was in fact a physical adsorption.

CONCLUSION

The present study was conducted to evaluate the feasibility of MON-NP for AMO removal from aqueous solutions. Batch adsorption studies were performed as a function of contact time, initial AMO concentration and adsorbent dose and influence of other interfering anions. AMO sorption kinetics was well fitted by pseudo-second-order kinetic model. The maximum sorption capacity of MON-NP for AMO removal was found to be 39.41 at $25 \pm 2^\circ\text{C}$. The AMO sorption has been well explained using Langmuir isotherm model. Results from this study demonstrated the potential utility of MON-NP for AMO removal from water.

ACKNOWLEDGEMENT

The authors are grateful from Student research committee of Zahedan University of Medical Sciences because of supporting of this research.

CONFLICT OF INTEREST

The authors declare no conflict of interest.

ABBREVIATIONS

MON-NP: Montmorillonite Nanoparticles; AMO: Ciprofloxacin.

REFERENCES

- Liu Z, Xie H, Zhang J, Zhang C. Sorption removal of cephalixin by HNO_3 and H_2O_2 oxidized activated carbons. *Sci China Chem.* 2012;55(9):1959-67.
- Liu H, Liu W, Zhang J, Zhang C, Ren L, Li Y. Removal of cephalixin from aqueous solution by original and Cu (II)/Fe (III) impregnated activated carbons developed from lotus stalks kinetics and equilibrium studies. *J Hazard Mater.* 2011;185(2-3):1528-35.
- Yu F, Li Y, Han S, Jie Ma J. Adsorptive removal of antibiotics from aqueous solution using carbon Materials. *Chemosphere.* 2016;153:365-85.
- Zhang L, Song X, Liu X, Yang L, Pan F. Studies on the removal of tetracycline by multi-walled carbon nanotubes. *Chem Eng J.* 2011;178:26-33.
- Azarpira H, Mahdavi Y, Khaleghi O. Thermodynamic Studies on the Removal of Metronidazole Antibiotic by Multi-Walled Carbon Nanotubes. *Pharm Lett.* 2016;8(11):107-3.
- Balarak D, Mostafapour FK, Bazrafshan E, Saleh TA. Studies on the adsorption of amoxicillin on multi-wall carbon nanotubes. *Water Sci Technol.* 2017;75(7):1599-606.
- Choi KJ, Kim SG, Kim SH. Removal of antibiotics by coagulation and granular activated carbon filtration. *J Hazard Mater.* 2008;151(1):38-43.
- Zhang W, He G, Gao P, Chen G. Development and characterization of composite nanofiltration membranes and their application in concentration of antibiotics. *Sep Purif Technol.* 2003;30(1):27-35.
- Ahmadi S, Banach A, Mostafapour FK. Study survey of cupric oxide nanoparticles in removal efficiency of ciprofloxacin antibiotic from aqueous solution: Adsorption isotherm study. *Water Sci Technol.* 2017;89:297-303.
- Balarak D, Mostafapour FK. Photocatalytic degradation of amoxicillin using UV/Synthesized NiO from pharmaceutical wastewater. *Indones J Chem.* 2019;19(1):211-8.
- Gao J, Pedersen JA. Adsorption of Sulfonamide Antimicrobial Agents to Clay Minerals. *Environ Sci Technol.* 2005;39(24):9509-16.
- Peterson JW, Petrasky LJ, Seymour MD, Burkhardt RS, Schuilinga AB. Adsorption and breakdown of penicillin antibiotic in the presence of titanium oxide nanoparticles in water. *Chemosphere.* 2012;87(8):911-7.
- Ghauch A, Tuqan A, Abou AH. Antibiotic removal from water: Elimination of amoxicillin and ampicillin by microscale and nanoscale iron particles. *Environ Pollut.* 2009;157(5):1626-35.
- Tavassoli P, Bazrafshan E, Mostafapour FK, Maghsoodi Z. Efficiency of UV Activated Sulfate in Removal of Ofloxacin from Aqueous Solutions. *J Mazandaran Univ Med Sci.* 2018;28(159):116-29.
- Ji L, Chen W, Duan L, Zhu D. Mechanisms for strong adsorption of tetracycline to carbon nanotubes: A comparative study using activated carbon and graphite as adsorbents. *Environ Sci Technol.* 2009;43(7):2322-7.
- Alexy R, Kumpel T, Kummerer K. Assessment of degradation of 18 antibiotics in the closed bottle test. *Chemosphere.* 2004;57(6):505-12.
- Yue QY, Li Q, Gao BY, Yuan AJ, Wang Y. Formation and characteristics cationic-polymer/ bentonite complexes of as adsorbents for dyes. *Appl Clay Sci.* 2007;35(3-4):268-75.
- Rytwo G, Huterer-Harari R, Dultz S, Gonen Y. Adsorption of fast green and erythrosin-B to montmorillonite modified with crystal violet. *J Therm Anal Calor.* 2006;84(1):225-31.
- Balarak D, Azarpira H. Rice husk as a Biosorbent for Antibiotic Metronidazole Removal: Isotherm Studies and Model validation. *Int J ChemTech Res.* 2016;9(7):566-73.
- Carabineiro A, Thavorn-Amornsri T, Pereira F, Figueiredo L. Adsorption of ciprofloxacin on surface modified carbon materials. *Water Res.* 2011;45(15):4583-91.
- Hu D, Wang L. Adsorption of amoxicillin onto quaternized cellulose from flax noil: Kinetic, equilibrium and thermodynamic study. *J Taiwan Inst Chem Eng.* 2016;64:227-34.
- Gao Y, Li Y, Zhang L, Huang H, Hu J, Shah SM, *et al*. Adsorption and removal of tetracycline antibiotics from aqueous solution by graphene oxide. *J Colloid Interface Sci.* 2012;368(1):540-6.
- Kerkez-Kuyumcu Ö, Bayazit SS, Salam MA. Antibiotic amoxicillin removal from aqueous solution using magnetically modified graphene nanoplatelets. *J Ind Eng Chem.* 2016;35:225-34.
- Ghauch A, Tuqan A, Assi HA. Elimination of amoxicillin and ampicillin by micro scale and nano scale iron particles. *Environ Pollut.* 2009;157:1626-35.

25. Kim SH, Shon HK, Ngo HH. Adsorption characteristics of antibiotics trimethoprim on powdered and granular activated carbon. *J Ind Eng Chem.* 2010;16(3):344-9.
26. Adrianoa WS, Veredasb V, Santanab CC, Gonçalves LRB. Adsorption of amoxicillin on chitosan beads: Kinetics, equilibrium and validation of finite bath models. *Chem Eng J.* 2005;27(2):132-7.
27. Gao Y, Li Y, Zhang L, Huang H, Hu J, Shah SM, *et al*. Adsorption and removal of tetracycline antibiotics from aqueous solution by graphene oxide. *J Colloid Interface Sci.* 2012;368(1):540-6.
28. Ghauch A, Tuqan A, Assi HA. Elimination of amoxicillin and ampicillin by micro scale and nano scale iron particles. *Environ Pollut.* 2009;157:1626-35.
29. Senthilkumaar S, Varadarajan PR, Porkodi K, Subbhuraam CV. Adsorption of methylene blue onto jute fiber carbon: Kinetics and equilibrium studies. *J Colloid Interface Sci.* 2005;284(1):78-82.
30. Aksu Z, Tunc O. Application of biosorption for Penicillin G removal: Comparison with activated carbon. *Process Biochemistry.* 2005;40(2):831-47.
31. Guler UA, Sarioglu M. Removal of tetracycline from wastewater using pumice stone: Equilibrium, kinetic and thermodynamic studies. *J Environ Health Sci Eng.* 2014;12(1):79-87.

Article History: Submission Date : 20-02-2020; Revised Date : 01-03-2020; Acceptance Date : 14-04-2020.

Cite this article: Balarak D, Ganji F, Chandrika K, Haseeb S. Montmorillonite Nanoparticles Effectiveness in Removal of Amoxicillin from Water Solutions. *Int. J. Pharm. Investigation.* 2020;10(2):122-6.